

New Developments with C-Mn-Ni in High-Strength Steel Weld Metals — Part B, Mechanical Properties

Mechanical properties of shielded metal arc welds, with varying compositions of carbon, manganese, and nickel were explained in terms of the relative amounts of different microstructural constituents

BY E. KEEHAN, L. KARLSSON, H.-O. ANDRÉN, AND L.-E. SVENSSON

ABSTRACT. Microstructure and properties have been studied for high-strength steel weld metals with variations in carbon, manganese, and nickel. Based on neural network modeling, experimental welds were made using shielded metal arc welding with manganese at 0.5 or 2.0 wt-% and nickel at 7 or 9 wt-%. Additional welds were made where carbon was varied between 0.03 and 0.11 wt-%. Generally there was very good agreement between the recorded mechanical properties and the neural network predictions. A combination of high nickel and manganese was positive for strength but very negative for impact toughness, while manganese reductions lead to large impact toughness increases. Carbon additions up to 0.11 wt-% were found to increase yield strength to over 900 MPa while still maintaining toughness at over 60 J at -100°C . Mechanical properties of the weld metals could be rationalized in terms of their relative amounts of the different microstructural constituents. Martensite provided the highest strength and reasonable toughness. Upper and lower bainite contributed to very good toughness and high strength. The least beneficial properties were found in the high-manganese variants due to a combination of primarily coarse-grained coalesced bainite and martensite. This combination of microstructural constituents resulted in poor toughness, relatively high yield strength, and the highest tensile strength. Furthermore, increasing contents of manganese and nickel resulted in a significant lowering of A_{c1} , thereby contributing to poorer impact toughness as a consequence of less tempering in reheated regions. The optimal combination of strength and impact toughness were found at 0.5 manganese

and 7 nickel with intermediate carbon levels, resulting in an easily tempered, fine scale mixture of upper and lower bainite together with some martensite.

Introduction

There has been ongoing development in high-strength steel weld metals with the aim of increasing strength while maintaining acceptable toughness since the 1960s. Studies have mainly focused on welding processes that offer flexibility such as shielded metal arc welding (SMAW). Research has been carried out based on fundamental understanding of the effects of alloying on phase transformations and microstructure to develop new improved compositions. Ultimately the aim has been to achieve weld metal properties that surpass established commercial weld metals and show less sensitivity to welding parameters (Ref. 1).

In the majority of high-strength steel weld metals investigated previously, the typical compositions have been C less than 0.2 wt-%, Ni less than 4 wt-%, and Mn less than 4 wt-% (Refs. 2–19). These compositions have been used with a variety of welding processes and generated yield strengths ranging from below 500 MPa to above 1000 MPa with good impact toughness mostly achieved at lower yield strengths. Focusing on positive results with SMAW, Lord (Ref.

12) found that nickel additions from 3 to 4 wt-% at decreasing Mn levels between 1.1 and 0.8 wt-% were good for toughness with minor losses of strength. It was found that toughness increased from 63 to 74 J at -60°C while yield strength decreased from 837 to 809 MPa (Ref. 12).

This paper is the second of a two-part report on an investigation of high-strength steel weld metals with variations in nickel, manganese, and carbon. In Part A, with Lord's results as a starting point (Ref. 12), neural network modeling (Refs. 20–22) was employed to allow the effect of a wide variety of parameters to be investigated quickly (Ref. 23). Based on simulations, experimental weld metals were produced with nickel at 7 or 9 wt-%, manganese at 0.5 or 2 wt-%, and carbon was varied between 0.03 and 0.11 wt-%. The exact compositions and welding parameters are presented in Table 1. The weld metals were named according to their alloying content and interpass temperature. The nickel content is 7 or 9 wt-%, and 0.5 or 2 wt-% is the manganese content, L, M, H are the carbon contents of 0.03, 0.06, or 0.11 wt-% respectively, and 200° or 250°C is the interpass temperature. Using high-resolution microstructural characterization techniques, it was found that at 7 and 9 wt-% Ni along with 2 wt-% Mn the microstructure was a mixture of upper and coalesced bainite at dendrite core regions while martensite was found at interdendritic regions. Reducing Mn content to 0.5 wt-% promoted more upper and lower bainite, while increasing C from 0.03 to 0.11 wt-%, promoted martensite (Refs. 23–26).

This article (Part B) focuses on the mechanical properties, and comparisons are made to the neural network predictions. In addition, the recorded mechanical properties are explained in terms of the microstructures previously characterized in Part A (Ref. 23) and elsewhere (Refs. 24–26).

KEYWORDS

High-Strength Steel
Neural Networks
Modeling
Mechanical Properties
Shielded Metal Arc
SMAW

E. KEEHAN and L. KARLSSON are with ESAB AB, Gothenburg, Sweden. H.-O. ANDRÉN and L.-E. SVENSSON are with Department of Applied Physics, Chalmers University of Technology, Gothenburg, Sweden.

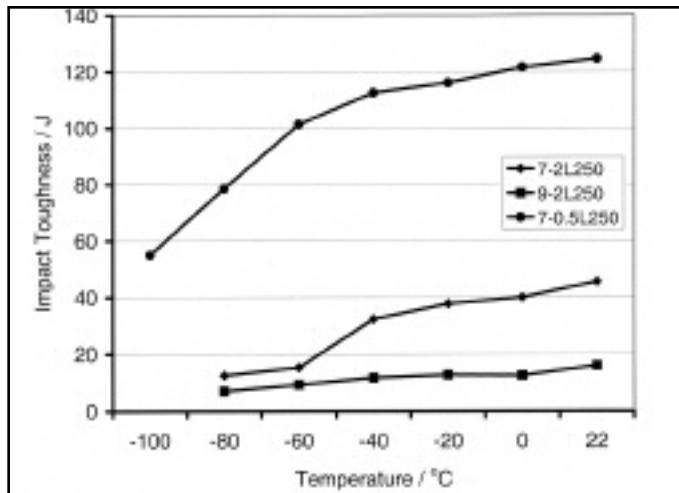


Fig. 1 — Charpy impact toughness plots showing the effect of increasing Ni from 7 to 9 wt-% and the effect of reducing Mn from 2 to 0.5 wt-%.

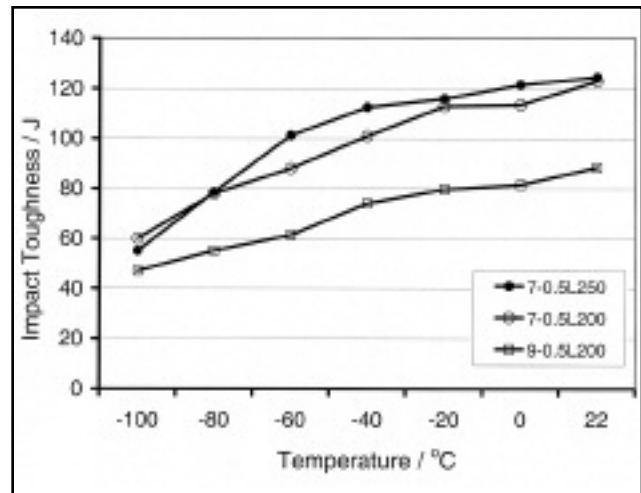


Fig. 2 — Impact toughness plots illustrating the effect of increasing Ni from 7 to 9 wt-% with Mn level at 0.5 wt-%. Also shown is the effect of increasing interpass temperature for the 7-Ni weld metals.

Table 1 — Welding Parameters and Chemical Composition

Weld Metal	7-2L250	9-2L250	7-0.5L250	7-0.5L200	9-0.5L200	7-0.5M200	7-0.5H200
E/kJ mm ⁻¹	1.2	1.2	1.0	1.3	0.7	1.4	1.3
IPT/°C	250	250	250	200	200	200	200
t 8/5/s	12	11	10	10	5	11	10
C*	0.032	0.031	0.024	0.030	0.026	0.061	0.110
Mn	2.02	2.11	0.64	0.61	0.37	0.56	0.53
Ni	7.23	9.23	6.60	6.11	8.67	6.84	7.04
Cr	0.47	0.48	0.21	0.16	0.20	0.15	0.14
Si	0.25	0.27	0.35	0.40	0.34	0.34	0.38
S*	0.008	0.008	0.008	0.009	0.008	0.006	0.007
P	0.011	0.011	0.012	0.010	0.007	0.011	0.008
Mo	0.63	0.64	0.40	0.38	0.41	0.35	0.40
V	n/a	n/a	n/a	0.02	n/a	0.01	0.02
Cu	0.03	0.03	0.03	0.02	0.01	0.01	n/a
O/ppm*	380	340	400	340	367	350	260
N/ppm*	250	260	197	150	130	160	100

Welding parameters presented are energy input (E), interpass temperature (IPT), and the estimated cooling time between 800 and 500°C ($t_{8/5}$) calculated from WeldCalc (Ref. 31). Composition is in wt-% unless otherwise stated. "*" indicates elements analyzed using Leco Combustion equipment and "n.a." are elements not analyzed.

Table 2 — Tensile Properties of the Different Weld Metals

	7-2L250	9-2L250	7-0.5L250	7-0.5L200	9-0.5L200	7-0.5M200	7-0.5H200
YS/MPa	795	848	721	777	827	858	912
UTS/MPa	1006	1051	823	831	895	895	971
A5/%	14.80	13.10	21.30	22.00	18.30	18.00	18.00

Experimental Procedures

The welded joints were made according to ISO 2560 using 20-mm plates with a backing strip. The joints were buttered prior to the deposition of the experimental weld metals that took place in 33-cm runs with two or three runs per layer.

Charpy impact testing and tensile testing were performed in compliance with standard EN 10045-1. For Charpy testing, transverse specimens were machined hav-

ing dimensions 55 × 10 × 10 mm. These were then notched perpendicular to the welding direction in the weld metal center and two or three specimens were tested at each temperature. Tensile specimens were machined longitudinally from the center of the weld deposits with a specimen diameter of 10 mm and a gauge length of 70 mm. Hardness measurements were carried out in cross sections of the joint perpendicular to the welding direction using Vickers method with a 10-kg load (HV10),

starting in the last bead and then proceeding into the joint center, with 1 mm in distance between the indentations.

Results

Strength and Impact Toughness

The results of Charpy impact toughness tests are plotted in Figs. 1–3. Typically, the scatter was less than ±3 J and in no case larger than ±5 J. Figure 1 shows

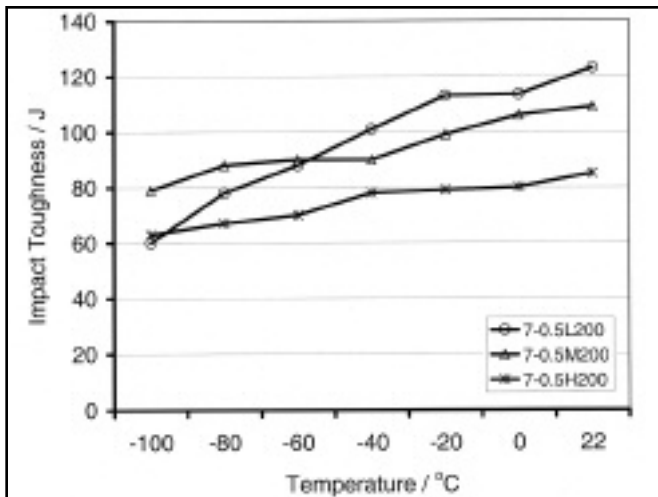


Fig. 3 — Impact toughness plots that show the effect of increasing carbon from 0.03 to 0.11 wt-% at 7 wt-% Ni and 0.5 wt-% Mn.

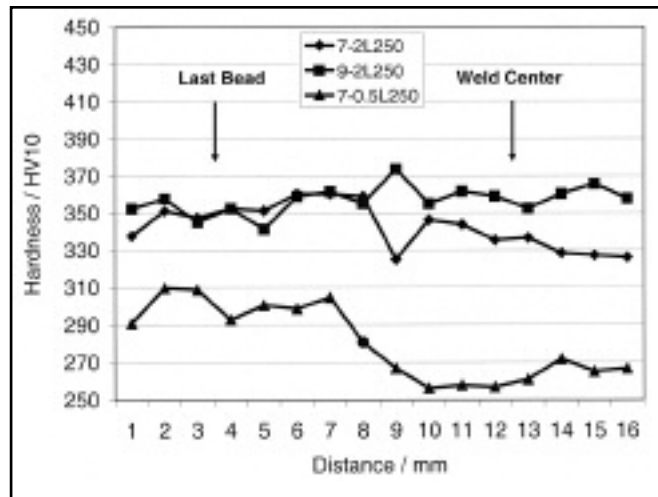


Fig. 4 — A comparison of hardness measurements that show the effect of increasing Ni from 7 to 9 wt-% and the effect of reducing Mn from 2 to 0 wt-% at 7 wt-% Ni.

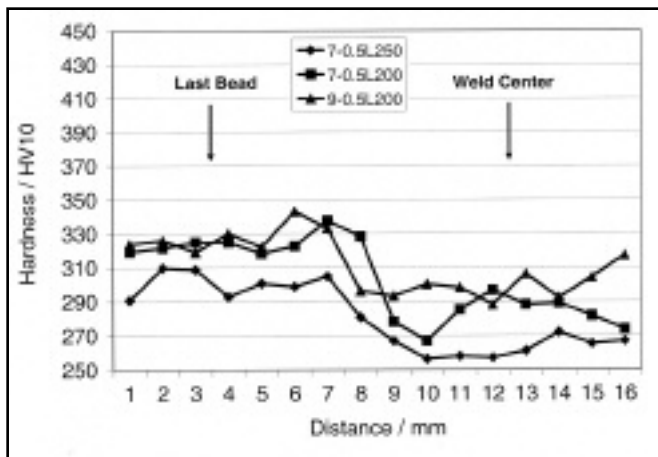


Fig. 5 — Hardness plots showing the effect of increasing Ni from 7 to 9 wt-% with Mn levels 0.5 wt-%. Also shown is the effect of reducing interpass temperature at a Mn content of 0.5 wt-%.

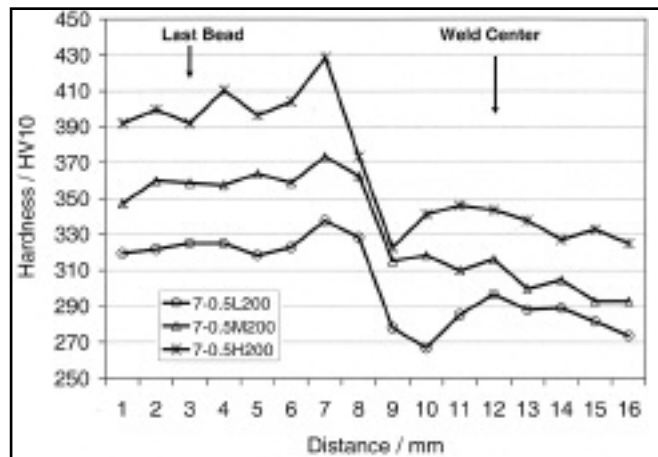


Fig. 6 — The effect on hardness of increasing C from 0.03 to 0.11 wt-% at 7 wt-% Ni and 0.5 wt-% Mn.

the results from the first three alloys welded with an interpass temperature of 250°C. Comparing 7-2L250 and 9-2L250, a lowering of impact toughness by increasing Ni from 7 to 9 wt-% at a Mn level of 2.0 wt-% is observed. However, comparing 7-0.5L250 with 7-2L250, a large increase in impact toughness was measured at all test temperatures as a result of reducing Mn content. An average increase of over 80 J was recorded at each test temperature down to -60°C. The tensile properties for these weld metals are presented in Table 2. It is seen that 7-2L250 and 9-2L250, which had poor impact toughness, recorded relatively high yield strength (YS) of 795 and 848 MPa, respectively, and ultimate tensile strength (UTS) more than 1000 MPa. Weld metal 7-0.5L250, which showed the higher impact toughness, recorded a relatively low strength with UTS at 823 MPa and YS at 721 MPa.

Weld metal 7-0.5L250 also recorded good elongation with a value of 21%.

With a view to increasing strength, it was decided to lower interpass temperature to 200°C in order to promote faster cooling. Comparing 7-0.5L250 with 7-0.5L200, which have similar compositions, yield strength increased from 721 to 777 MPa. However, this trend was limited with the UTS, which only increased from 823 to 831 MPa. The impact toughness plotted in Fig. 2 was maintained very well with more than 100 J recorded at -40°C. Increasing nickel from 7 to 9 wt-% in combination with low manganese and a 200°C interpass, increased YS by 50 MPa and UTS by 64 MPa, where 895 MPa was recorded for UTS (Table 2). These changes were accompanied by a decrease in impact toughness, but only to 75 J at -40°C — Fig. 2. A common feature of the low-Mn weld metal was maintaining good impact tough-

ness down to at least -100°C.

Given the results of the modeling and the recorded mechanical properties with the first six alloys, it was decided to set Mn at 0.5 wt-%, Ni at 7 wt-%, and use an interpass temperature of 200°C. The effects of carbon additions on mechanical properties were then examined with the deposition of 7-0.5M200 and 7-0.5H200. From Table 2, it is seen that carbon additions were positive to YS and UTS. 7-0.5H200 recorded the best YS of all alloys studied with 912 MPa achieved at a carbon level of 0.11 wt-%. Given the strength, high impact toughness was also recorded with over 60 J at -100°C — Fig. 3. Surprising was that although the higher-carbon weld metals showed lower impact toughness than 7-0.5L200 at room temperature, they maintained impact toughness to lower temperatures and both actually surpassed 7-0.5L200 at -100°C.

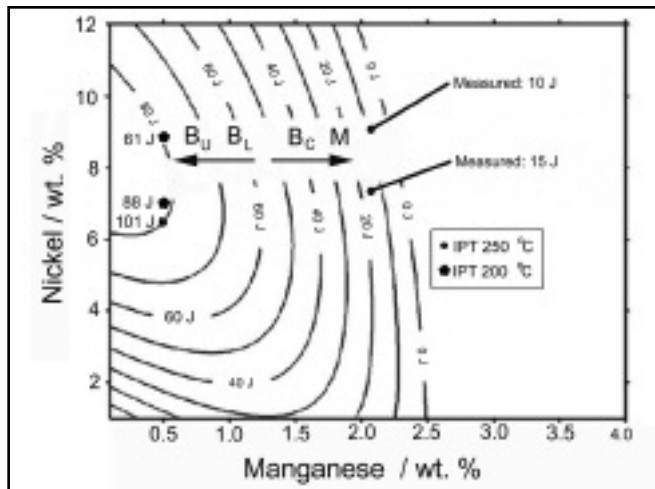


Fig. 7 — Comparison between recorded and predicted impact toughness at -60°C as a function of manganese and nickel content. See Part A (Ref. 23) for details of the modeling. Upper bainite is B_U , lower bainite is B_L , coalesced bainite is B_C and martensite is M . These were the observed microstructures from microstructural investigations.

Hardness

Hardness measurements for all weld metals are presented in Figs. 4–6. The measurements were made starting at the top of the last bead and then proceeding down through the center of the welded joint. Looking at 7-2L250 and 9-2L250 shown in Fig. 4, minor fluctuations are seen in the recorded values but generally hardness levels are high and fairly constant throughout the welded joint. In contrast, 7-0.5L250, which was the softer of the three alloys, lost hardness very much in the center of the welded joint. This latter weld alloy also had the best impact toughness of the three. The effect on hardness of decreasing interpass temperature can be studied by comparing 7-0.5L250 and 7-0.5L200, as shown in Fig. 5. It is found that decreasing interpass temperature gives an increase in hardness. Comparing 9-0.5L200 with 7-0.5L200, it is seen that nickel additions at 0.5 wt-% Mn produce a marginally harder weld metal. In Fig. 6, as carbon increases from 0.03 to 0.11 wt-%, hardness levels increase as expected. 7-0.5H200 had the highest hardness levels in the last bead but it also lost the most hardness of all alloys as the central regions of the welded joint were encountered.

Discussion

Modeling

A comparison between the recorded mechanical properties, the neural network predictions, and the characterized microstructural constituents are presented in Figs. 7 and 8. Generally, good agreement was found between the experi-

mental data and the predicted values. The contour plot of impact toughness as a function of Mn and Ni content was more or less proven correct. It was found that impact toughness was underestimated with 7 wt-% Ni combined with 0.5 wt-% Mn. For weld metal 9-0.5L200, there was a slight overestimation between predicted and recorded toughness but this is to be expected since the predictions are for an interpass temperature of 250°C . Yield strength as a function of carbon content was found to be slightly overestimated but recorded results were mostly within the error limits. Impact toughness as a function of carbon content was found to be marginally underestimated. Overall, it can be concluded that the models were reliable in predicting the mechanical properties for the studied weld metal compositions, and as expected, most accurate within compositional regions where input data were available.

Strength vs. Impact Toughness

In Fig. 9, yield strength and ultimate tensile strength are plotted vs. impact toughness at room temperature. Normally, it is found that there is a good correlation between tensile strength and impact toughness in that an increased tensile

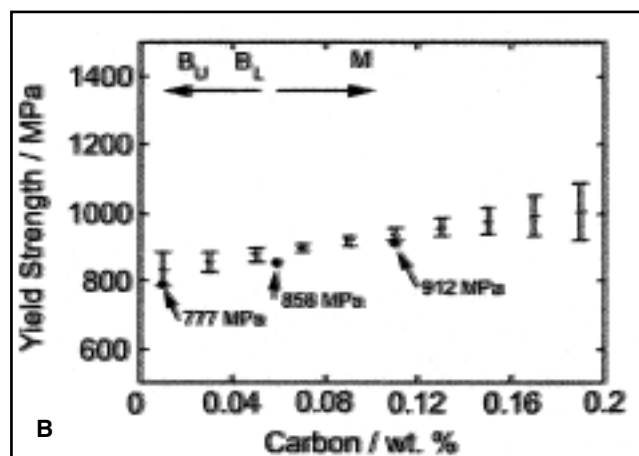
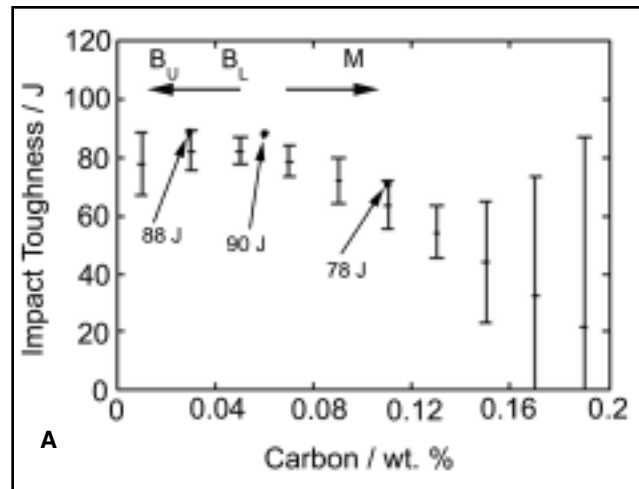


Fig. 8 — A comparison between (a) the recorded impact toughness at -60°C along with (b) yield strength vs. the neural network predictions as a function of carbon content for 7 wt-% Ni combined with 0.5 wt-% Mn. Also shown are the microstructural changes in relation to the increasing carbon content as was observed with microstructural investigations. B_U is upper bainite, B_L is lower bainite and M is martensite.

strength results in decreased impact toughness. This behavior was indeed observed for the presently studied weld metals, showing a nearly linear relationship between impact toughness and tensile strength — Fig. 9. However, comparing weld metals 9-2L250, 7-2L250, 9-0.5L200 and 7-0.5M200, it can be seen that there is a large variation in toughness at similar yield strengths. It can be noted that the high-Mn weld metals, having a wide gap between yield strength and tensile strength (Table 2), are those having the lowest impact toughness at a given yield strength level. The variation may be attributed to differences in the microstructure (Ref. 23), as is discussed in more detail in the following section.

Constitutional Diagram

Figure 10 presents a constitutional di-

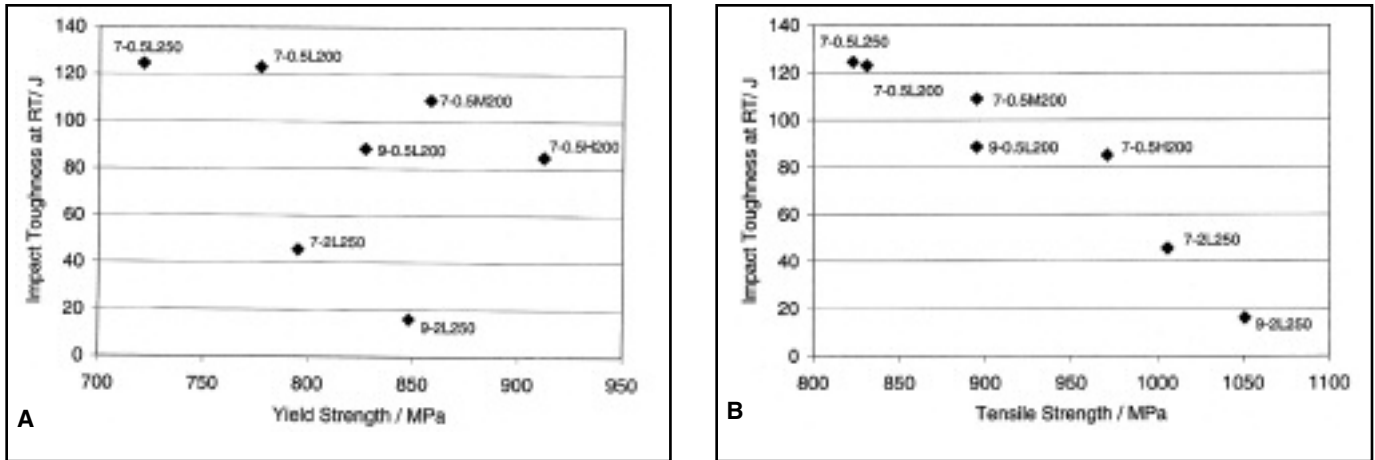


Fig. 9 — Impact toughness as a function of the following: A — Yield strength ; B— ultimate tensile strength.

Table 3 — A Summary of the Main Microstructural Constituents Reported in Part A

Weld Metal	Dendrite Core Regions	Interdendritic Regions
7-2L250	Upper bainite and coalesced bainite	Martensite
9-2L250	Upper bainite and coalesced bainite	Martensite
7-0.5L250	Upper and lower bainite	Upper and lower bainite with small amounts of martensite
7-0.5L200	Upper and lower bainite	Upper and lower bainite with martensite
7-0.5H200	Mainly martensite with some bainite	Mainly Martensite

agram (microstructure as a function of nickel and manganese content) that was introduced in Part A (Ref. 23). This was based on microstructural observations, dilatometry experiments, martensite start temperature (M_s) and bainite start temperature (B_s) predictions, and literature. The martensite composition start line is plotted with values taken from literature (Ref. 27). Also shown is the line where B_s and M_s are equal as predicted from empirical equations (Refs. 28, 29). With alloying contents around this line coalesced bainite was observed with 7 and 9 wt-% Ni in combination with 2 wt-% Mn. For compositions above the line martensite becomes the dominant constituent, whereas upper and lower bainite becomes the main constituents below the line (Ref. 23).

Correlating Properties to Microstructure

From the studies carried out, it is clear that the amount of C, Mn, and Ni affects the microstructure that, in turn, determines the mechanical properties. A short summary of the results are made (Table 3) and it is then shown that strength, elongation, and impact toughness can be rationalized in terms of

the microstructural constituents.

A combination of 7 wt-% Ni and 2 wt-% Mn gave poor toughness but good strength. Nickel additions with this Mn content were found to increase strength slightly but decrease toughness even further. From microstructural examinations, a combination of upper bainite and coalesced bainite with a large grain size formed in dendrite core regions with martensite present at interdendritic regions. Large amounts of coalesced bainite were only observed in these weld metals. Overall there was no major difference in the microstructure between 7-2L250 and 9-2L250. For these weld metals, hardness was maintained at similar levels throughout the welded joint with only a slight decrease in reheated regions — Fig. 4.

As has previously been observed at 3.5 wt-% Ni (without Cr or Mo additions) (Ref. 18), impact toughness was very sensitive to Mn content with a dramatic increase obtained when Mn was reduced from 2 to 0.5 wt-% — Fig. 7. It was found that weld metal 7-0.5L250 had the highest impact toughness but the lowest yield strength (721 MPa) and tensile strength (824 MPa) of the weld metals tested. There was also a

large decrease in hardness compared to the high-Mn weld metals, and a significant decrease in reheated regions — Fig. 4. Microstructural studies revealed that reducing Mn content was found to promote austenite transformation at higher temperatures with more upper and lower bainite forming. Decreasing the interpass temperature to 200°C was found to increase hardness and reduce toughness marginally, which was attributed to faster cooling and greater amounts of martensite.

Increasing C to 0.11 wt-% caused yield and tensile strength to increase while impact toughness was maintained — Fig. 8. Austenite was stabilized to lower transformation temperatures with an increasingly finer microstructure forming and martensite becoming the dominating constituent. As expected, hardness increased with the greater amounts of martensite. The decrease in hardness on reheating became more pronounced with increasing C levels, which is typical of a martensitic microstructure.

The amount of tempering, which is largely controlled by Ac_1 and Ac_3 , also has an important effect on the mechanical properties in reheated regions of these weld metals. It was observed that significant softening takes place in reheated beads with weld metal 7-0.5H200 (which is mainly martensitic) and with 7-0.5L250 (which is primarily a mixture of upper and lower bainite). Both of these weld metals had relatively high Ac_1 and Ac_3 values (Ref. 23). However, with weld metals 7-2L250 and 9-2L250 with lower Ac_1 and Ac_3 temperatures (Ref. 23) hardness was maintained into reheated regions. This can be attributed to less tempering in regions reheated to below Ac_1 due to slower kinetics at lower temperatures and most likely to the formation of more fresh un-

tempered microstructural constituents. Furthermore, it is likely that the observed precipitation in the tempered coalesced bainite (Ref. 23) contributes to the higher hardness of these weld metals.

Summarizing the above results, the effects of microstructure on the mechanical properties can be rationalized as follows:

A fine, mainly martensitic microstructure (e.g. 7-0.5H200) gave high yield strength and tensile strength with little difference between the two. In addition, acceptable impact toughness was recorded.

A mixture of mainly upper and lower bainite (e.g. 7-0.5L200) gave lower yield and tensile strengths with a small difference between the two values. For this combination of microstructural constituents, very good impact toughness was recorded.

Coalesced bainite combined with upper bainite and significant amounts of martensite (7-2L250 and 9-2L250) gave relatively high yield strength and a very high tensile strength but poor elongation. Most significantly, very poor impact toughness was recorded. This latter mixture of coalesced bainite combined with upper bainite and martensite is obviously unfavorable. It can be assumed that yield strength is determined by the relatively weaker coarse-grained coalesced bainite and tensile strength by martensite. The poor impact toughness can most likely be attributed to the combined effect of easily cleaved coalesced bainite and tempering characteristics.

In conclusion, designing high-strength steel weld metals that have a combination of both high yield strength and good impact toughness is a complex task. In terms of microstructural constituents, it is clear from this study and literature that interesting properties can be obtained with different proportions of upper and lower bainite and martensite. However, compositional regions where the bainite and martensite start temperatures are close, promoting coarse-grained, relatively weak and brittle, coalesced bainite should be avoided. It remains to be clarified whether the microstructural inhomogeneity (a banded microstructure) introduced by the higher alloying contents and austenitic solidification can be used to optimize properties. It is clear though from a parallel study on the 7Ni, 0.5Mn weld metal (Ref. 30) that the high alloying content resulted in a robust weld metal in the sense that large variations in welding parameters had little effect on strength and impact toughness. The identification of coalesced bainite and its effects on mechanical properties helped to clarify the relation between properties and microstructure. Nevertheless, further work exploring effects of other alloying elements is clearly needed

to make understanding more complete and facilitate development of further-improved high-strength steel weld metal compositions.

Conclusions

Based on neural network modeling, experimental welds were produced using SMAW with Mn at 0.5 or 2.0 wt-% and Ni at 7 or 9 wt-%. Additional welds were made where carbon was varied between 0.03 and 0.11 wt-% with Mn set at 0.5wt-% and Ni at 7 wt-%. Generally, there was very good agreement between the recorded mechanical properties and the neural network predictions for these weld metal compositions.

A combination of high nickel and manganese was positive for strength but very negative for toughness. Poor toughness was attributed to the presence of coalesced bainite and relatively low Ac_1 and Ac_3 temperatures, which give less tempering within the welded joint.

Manganese reductions lead to large increases in toughness with a content of 7–9 wt-% Ni. Impact toughness of 113 J at -40°C , and yield strength of 721 MPa was recorded for 0.6 wt-% Mn and 6.6 wt-% Ni. Impact toughness gain was explained by the replacement of coalesced bainite with upper and lower bainite along with greater amounts of tempering due to higher Ac_1 and Ac_3 temperatures.

Carbon additions up to 0.11 wt-% increased yield strength to 912 MPa while still maintaining over 60 J toughness at -100°C . Carbon additions promoted a fine martensitic microstructure, increasing strength with limited loss of toughness.

Mechanical properties of the weld metals were explainable in terms of their relative amounts of the different microstructural constituents. Martensite was found to provide high strength and reasonable toughness, whereas upper and lower bainite contributed to very good toughness and somewhat lower strength. The coarse-grained coalesced bainite found for compositions with M_s and B_s close to each other was concluded to give relatively low strength and poor impact toughness.

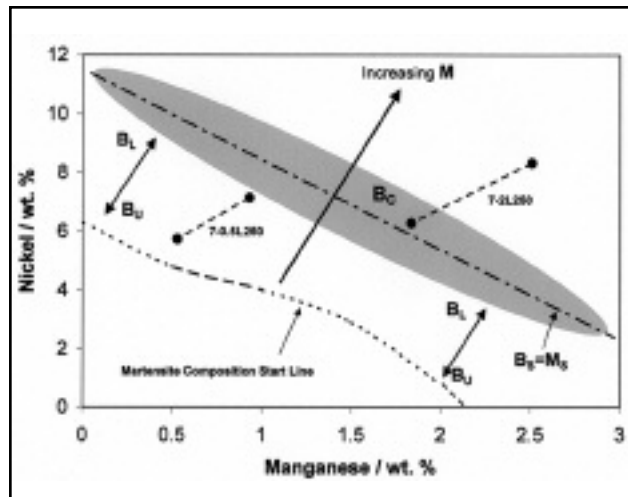


Fig. 10 — Constitutional diagram showing the weld metal microstructure as a function of Mn and Ni for a base composition of 0.034 C, 0.25 Si, 0.5 Cr, and 0.62 Mo. The martensite start composition line from literature is presented (Ref. 27) along with the line where B_s and M_s are equal according to standard empirical equations (Refs. 28, 29). Around these compositions coalesced bainite (B_C) is expected. Above martensite (M) becomes the main constituent, whereas the volume fraction of upper (B_U) and lower (B_L) bainite increases below this line as shown in Part A (Ref. 23). In 7-2L250 and 7-0.5L250 7 is the nickel content in wt-%, 0.5 or 2 wt-% is the manganese content, L is the carbon contents of 0.03 wt-%, and 250 is the interpass temperature in $^\circ\text{C}$.

Acknowledgments

M. Muruganath of the University of Cambridge is thanked for carrying out neural network modeling. H. K. D. H. Bhadeshia, also at the University of Cambridge, is thanked for fruitful discussions. ESAB AB is thanked for the production of experimental weld metals, permission to publish results, and financial support. Knowledge Foundation of Sweden is thanked for additional financial support.

References

1. Widgery, D. J., Karlsson, L., Muruganath, M., and Keehan, E. 2002. Approaches to the development of high-strength weld metals. *Proceedings 2nd Int. Symposium on High Strength Steel*. Stiklestad, Verdal, Norway: European Coal and Steel Community (ECSC), B-1049 Brussels, Belgium
2. Abson, D. J., and Pargeter, R. J. 1986. Factors influencing as-deposited strength, microstructure, and toughness of manual metal arc welds suitable for C-Mn steel fabrications. *International Metals Reviews* 31(4): 141–194.
3. Fairchild, D. P., Macia, M. L., Bangaru, N. V., and Koo, J. Y. 2003. Girth welding development for X120 linepipe. *ISOPE-2003: Thirteenth International Offshore and Polar Engineering Conference*. Honolulu, Hi, International Society of Offshore and Polar Engineers, Cupertino, Calif.,

editor@isope.org, <http://www.isope.org>

4. Farrar, R. A., and Harrison, P. L. 1987. Acicular ferrite in carbon-manganese weld metals: an overview. *J. Mater. Sci.* 22(11): 3812–3820.

5. Fleming, D. A., Bracarense, A. Q., Liu, S., and Olson, D. L. 1996. Towards developing a SMA welding electrode for HSLA 100 grade steel. *Welding Journal* 75(6): 171-s to 183-s.

6. Grong, O., and Matlock, D. K. 1986. Microstructural development in mild and low-alloy steel weld metals. *Int. Met. Rev.* 31(1): 27–48.

7. Harrison, P. L., and Farrar, R. A. 1981. Influence of oxygen-rich inclusions on the gamma arrow right alpha phase transformation in high-strength low-alloy (HSLA) steel weld metals. *Journal of Materials Science* 16(8): 2218–2226.

8. Kang, B. Y., Kim, H. J., and Hwang, S. K. 2000. Effect of Mn and Ni on the variation of the microstructure and mechanical properties of low-carbon weld metals. *ISIJ International (Japan)* 40(12): 1237–1245.

9. Lau, T. W., Sadowsky, M. M., North, T. H., and Weatherly, G. C. 1987. Effect of nitrogen on the toughness of HSLA weld deposits. *Welding Metallurgy of Structural Steels*, International TMS/EWI Symposium. Denver, Colo.: Warrendale, Pa., Metallurgical Society of AIME (TMS).

10. Liao, J., Kametani, H., Okada, H., and Ikeuchi, K. 2001. Toughness of weld metals of 950 MPa high-strength steel. *7th Int. Symposium, Today and Tomorrow in Science and Technology of Welding and Joining*. Kobe, Japan, Japan Welding Society.

11. Lord, M. 1999. Design and modelling of ultra high strength steel weld deposits. *Materials Science and Metallurgy*. University of Cambridge: Cambridge, UK.

12. Lord, M., and Jennings, G. 1999. Effect

of interpass temperature on properties of high-strength weld metals. *Svetsaren (Sweden)* 54(1-2): 53–58.

13. McRobie, D. E., and Knott, J. F. 1985. Effects of strain and strain aging on fracture toughness of C-Mn [steel] weld metal. *Materials Science and Technology* 1(5): 357–365.

14. Svensson, L. E. 1999. Consumables for welding high strength steels. *Svetsaren* 54(1-2): 29–33.

15. Svensson, L. E., and Greftoft, B. 1990. Microstructure and impact toughness of C-Mn steel weld metals. *Welding Journal* 69(12): 454-s to 461-s.

16. Taylor, D. S., and Evans, G. M. 1983. Development of MMA electrodes for offshore fabrication. *Met. Constr.* 15(8): 438–443.

17. Wang, W., and Liu, S. 2002. Alloying and microstructural management in developing SMAW electrodes for HSLA-100 steel. *Welding Journal* 81(7): 132-s to 145-s.

18. Evans, G. 1990. The effect of nickel on the microstructure and properties of C-Mn all-weld metal deposits. *Oerlikon Schweissmittelungen*. 48(122): 18–35.

19. Evans, G. M., and Bailey, N. 1997. *Metallurgy of Basic Weld Metal*. Abington Publishing.

20. Bhadeshia, H. K. D. H. 1999. Neural networks in material science. *ISIJ International* 39(10): 966–979.

21. Mackay, D. J. C. 1992. *Neural Computation*. p. 415.

22. Mackay, D. J. C. 1992. *Neural Computation*. p. 448.

23. Keehan, E., Andrén, H. O., Karlsson, L., and Svensson, L.-E. 2006. New developments with C-Mn-Ni high-strength steel weld metals,

Part A. microstructure. *Welding Journal* 85(9): 200-s to 210-s.

24. Keehan, E., Karlsson, L., and Andrén, H.-O. 2006. Influence of C, Mn and Ni on strong steel weld metals: Part 1, effect of nickel content. *Science and Technology of Welding and Joining* 11: 1–8.

25. Keehan, E., Karlsson, L., Andrén, H.-O., and Bhadeshia, H. K. D. H. 2006. Influence of C, Mn, and Ni on strong steel weld metals: Part 2, impact toughness gain from manganese reductions. *Science and Technology of Welding and Joining* 11: 9–18.

26. Keehan, E., Karlsson, L., Andrén, H.-O., and Bhadeshia, H. K. D. H. 2006. Influence of C, Mn and Ni on strong steel weld metals: Part 3, increased strength from carbon additions. *Science and Technology of Welding and Joining*, 11: 18–24.

27. Zhang, Z., and Farrar, R. A. 1997. Influence of Mn and Ni on the microstructure and toughness of C-Mn-Ni weld metals. *Welding Journal* 76(5): 183-s to 196-s.

28. Honeycombe, R. W. K., and Bhadeshia, H. K. D. H. 1995. *Steel Microstructure and Properties*. 2nd ed, Edward Arnold, London, UK. p. 133.

29. Honeycombe, R. W. K., and Bhadeshia, H. K. D. H. 1995. *Steel Microstructure and Properties*. 2nd ed, Edward Arnold, London, UK. p. 103.

30. Karlsson, L., Keehan, E., Andrén, H.-O., and Bhadeshia, H. K. D. H. 2004. Development of high-strength steel weld metals — potential of novel high-Ni compositions. *Eurojoin* 5. Vienna, Austria.

31. SSAB, *WeldCalc*. 1998–99. Oxelösund, Sweden.

CALL FOR PAPERS

Papers are being requested for the European Symposium on Pressure Equipment, to be held Oct. 9–11, 2007, in Paris, at the Palias des Congres. The overall theme of the conference is “Equipment during fabrication and service: safety, competitiveness, innovation,” and session themes are 1) Design/Materials; 2) Fabrication, Welding, Inspection; and 3) Equipment in Service. **The deadline for submitting a one-page abstract in English or French is October 31, 2006.** More information is available on the following Web site: www.afiap.org. Abstracts should be sent to AFIAP- ESOPE 2007, F-92038 PARIS-LA DEFENSE Cedex, FRANCE.