

Stabilisation of Ferrite in Hot-Rolled δ -TRIP Steel

Hongliang Yi^{*}, Kyooyoung Lee[†] and H. K. D. H. Bhadeshia^{*‡}

^{*}Graduate Institute of Ferrous Technology (GIFT)
Pohang University of Science and Technology (POSTECH)
Pohang 790-784, Republic of Korea, cml.postech.ac.kr

[†]POSCO Technical Research Laboratories
Gwangyang-si, Jeonnam, Republic of Korea

[‡]University of Cambridge
Materials Science and Metallurgy, Cambridge CB2 3QZ, U.K.

Abstract

A steel has recently been designed to benefit from the deformation-induced transformation of retained austenite present in association with bainitic ferrite. It has as its major microstructural component, dendrites of δ -ferrite introduced during solidification. The δ -ferrite replaces the allotriomorphic ferrite present in conventional alloys of this kind. We examine here the stability of this δ -ferrite during heating into a temperature range typical of hot-rolling conditions. It is found that contrary to expectations from calculated phase diagrams, the steel becomes fully austenitic under these conditions, and that a better balance of ferrite promoting solutes is necessary in order to stabilise the dendritic structure. New alloys are designed for this purpose and are found suitable for hot-rolling in the two-phase field over the temperature range 900–1200°C.

1 Introduction

A δ -TRIP steel has an unconventional microstructure in which the major constituent is δ -ferrite which forms during solidification and is permanently retained after solidification [1]. The rest of the structure can be transformed into a mixture of bainitic ferrite and austenite which is stabilised by the partitioning of carbon between the two these two allotropic forms of iron. It is this austenite, which behaves as in conventional TRIP-assisted steels [2–10], and undergoes deformation induced-transformation to martensite and as a result enhances the ductility of the alloy. Hence the acronym TRIP, which stands for transformation-induced plasticity [11]. The steel has interesting properties in its as-cast state: an ultimate tensile strength of about 1000 MPa and a total elongation, almost all of which is uniform, of 23%.

There is a difficulty with the alloy design. In spite of cooling rates as slow as about 20 K s^{-1} , solid-state transformation after solidification is completed exhibits large deviations from equilibrium conditions [1]. Compositions which should, according to phase diagram calculations, show large quantities of δ -ferrite dendrites, often display zero or much reduced fractions on casting. This is because the austenite that forms during cooling by the solid-state transformation of cored δ -dendrites, does so without the required partitioning of substitutional solutes, particularly aluminium.

It is important in the δ -TRIP concept to maintain as far as is possible, the ferrite produced during solidification because its presence at all temperatures should improve its resistance spot-weldability. If the material fails to become fully austenitic in the heat-affected zone (HAZ), then it also becomes impossible to obtain a fully martensitic structure there. This should result in better welds because large gradients in properties in the affected region are known to dramatically reduce the shear resistance of spot welds [12]. Indeed, current TRIP-assisted steels are known to be difficult to spot-weld because of the production of fully martensitic regions in the HAZ.

The problem of retaining the δ -ferrite can of course be solved by adding aluminium in concentrations greater than required by equilibrium. This increases the fraction of δ -ferrite in the cast structure, even in the absence of equilibrium partitioning [13]. However, it is necessary to examine the stability of the δ -ferrite also in the reheated condition since the casting must ultimately be hot-rolled in order to produce the form required for potential applications, such as in the car industry. The purpose of the present work is to assess the capability of the alloy system to sustain the ferrite during the reheating required for the hot-rolling process, which is usually in the range $1200\text{--}900^\circ\text{C}$.

The purpose of the work presented here was to create a variant of the δ -TRIP steel in which the ferrite is retained during excursions to very high temperatures. It is hoped that this work will form the basis of a future development programme where the steel can be produced by hot-rolling with the required quantity of ferrite, followed by the formation of the mixture of bainitic ferrite and retained austenite in a continuous process.

2 Experimental Details

Phase diagrams were estimated using MTDATA [14] in combination with the TCFE (version 1.21) database. The alloys were manufactured as 34 kg ingots of dimensions $100 \times 170 \times 230\text{ mm}$ using a vacuum furnace. In one case, representing the final alloy choice, the ingot was reheated to 1200°C for rough rolling to make 25–30 mm slabs followed by air cooling. These slabs were then reheated to 1200°C (heating rate to 1200°C not monitored) and hot-rolled to 3 mm in thickness with the temperature always maintained above 900°C followed by cooling.

Optical microscopy samples were prepared using standard methods and etched in 2% nital. Heat-treatments were conducted on cylindrical dilatometric samples of diameter 5 mm and length 10 mm using a push-rod *BAHR DIL805* high-speed dilatometer with radio frequency induction heating; the equipment has been described elsewhere [15]. The sample temperature is measured by a thermocouple welded to its surface using a precision welder and jig supplied by the dilatometer manufacturer.

The cast structure of the alloy identified as ‘Alloy 2’ in Table 1 has been investigated previously [13] and hence its designation is maintained here in order to avoid confusion. The alloy is new melt of the original δ -TRIP design [1], needed to provide more material for experiments; the design emerged from the neural network and genetic algorithm analysis and the details are described fully in [1].

3 Reheating Experiments

The microstructure of the as-cast state of Alloy 2 is illustrated in Fig. 1 along with the calculated equilibrium phase diagram, which indicated that a large fraction of the δ -dendrites generated during solidification should, under equilibrium conditions, persist during reheating at all temperatures.

Samples of the steel were heated at 20°C s^{-1} to peak temperatures of 800, 850, 900, 1000, 1100 and 1290°C for 5 min; further samples were similarly heated to 1360, 1380 and 1400°C for 1 min. After the small holding period, the samples were all quenched at -80°C s^{-1} . The heat-treatments were conducted on the dilatometer. The heating rate and transformation times used here will be different from those practised in an industrial environment, but the difference is unlikely to be significant given the rapid rate of austenite formation at high temperatures.

Metallographic studies were conducted on all the samples but only selected examples are presented here. Fig. 2a shows the effect of heating to 800°C ; there is clear evidence for the partial transformation of pearlite into austenite so that quenching leads to martensite in the centres of the interdendritic regions where austenite-stabilising elements are partitioned [13]. The austenite that forms from pearlite then begins to penetrate the δ -dendrites. The amount of austenite obtained is inconsistent with the equilibrium phase diagram (Fig. 1), although these observations are not surprising given that the austenite grows without the required level of solute partitioning between the parent and product phases [13].

By 950°C , the δ -dendrite arms are no longer visible as uniform features, but on a microscopic scale consist of martensite and remnants of ferrite which are in the form of a network, presumably reflecting segregation patterns, Fig. 2b. The sample heat-treated to a peak temperature of 1100°C became almost fully austenitic, although the overall structure remained fine because of the pinning of austenite grain boundaries by remnants of ferrite, Fig. 3a. The ferrite content only recovered slightly when the peak temperature reached 1400°C , in a form reminiscent of the δ -ferrite, presumably following the solidification-induced chemical segregation patterns existing in the sample.

It is evident the alloy would not be suitable for a process in which substantial δ -ferrite must be retained in the microstructure during the hot-rolling process, even though the equilibrium phase diagram suggests otherwise. These large deviations from expectation make it difficult to design suitable alloys; in previous work [13] we used *DICTRA*, which allows growth to be modelled, to establish that the magnitudes of the kinetic effects are reasonable, but the method requires assumptions about shape and scale which make its use for alloy design in the present context difficult. Therefore, a pragmatic approach was adopted in which new alloys were designed based essentially on experience, with the broad aim of stabilising the ferrite.

4 New Alloys

Referring to Table 1 and using Alloy 2 as a reference, Alloy 3 is based on the removal of copper, which is an austenite-stabilising element. The silicon concentration is increased in Alloy 4 since both aluminium and silicon [16] have the same γ -loop forming tendency and hence favour the formation of δ -ferrite. Alloy 5 is based on a reduction in the manganese concentration, and Alloy 6 on a simultaneous reduction in Mn and increase in the silicon and aluminium concentrations. Alloy 7 has a lower Mn, high Si and particularly high Al concentrations. Phase diagram calculations for the new alloys are illustrated in Fig. 4; they show that the greatest potential for increasing the stability of δ -ferrite should be in Alloys 6 and 7.

Reheating experiments were conducted as described for Alloy 2 and quantitative data are presented in Fig. 6. δ -ferrite did not persist in Alloys 2–5 on reheating, but dendrites of this phase survived in Alloys 6 and 7, although the fraction of δ -ferrite is much less than expected from equilibrium, Fig. 7.

The microstructure after hot-rolling is illustrated in Fig. 8, where it is evident that there are two kinds of ferrite present, the first the δ -ferrite which has been elongated by deformation and then the allotriomorphic ferrite which precipitates as the temperature during rolling reduces towards 900°C. It is seen that the presence of ferrite at all temperatures maintains a fine austenite and ferrite grain structure.

5 Conclusions

The δ -TRIP alloy system is based on the use of a relatively large concentration of aluminium, which should lead to the formation of a substantial quantity of ferrite dendrites at equilibrium. Much of this ferrite which forms during solidification should in principle resist transformation into austenite when the steel is heated to the high temperatures typical of hot-rolling deformation. That it does not do so in practice has been shown in previous work [13] to be due to the fact that austenite is able to form by solid state transformation from δ -ferrite without the required level of partitioning of solutes, particularly aluminium.

In the present work it has been demonstrated that suitable alloys in which the δ -ferrite remains in the microstructure over the range 900–1200°C have been designed by increasing the aluminium and silicon concentrations, accompanied by a reduction in the manganese and copper contents. It has been possible therefore to produce a rolled variant of the alloy which will be used in further investigations towards the commercialisation of the steel on a continuous production line.

Acknowledgements

We are grateful to Professor Hae-Geon Lee of the Graduate Institute of Ferrous Technology for the provision of laboratory facilities at POSTECH, and to POSCO for help and support. The work is

partly supported by the Korea Science and Engineering Foundation under the context of the World Class University programme, project number R32-2008-000-10147-0.

References

- [1] S. Chatterjee, M. Muruganath, and H. K. D. H. Bhadeshia. δ -TRIP steel. *Materials Science and Technology*, 23:819–827, 2007.
- [2] O. Matsumura, Y. Sakuma, and H. Takechi. Enhancement of elongation by retained austenite in intercritical annealed 0.4C-1.5Si-0.8Mn steel. *Transactions of the Iron and Steel Institute of Japan*, 27:570–579, 1987.
- [3] O. Matsumura, Y. Sakuma, and H. Takechi. TRIP and its kinetic aspects in austempered 0.4C-1.5Si-0.8Mn steel. *Scripta Metallurgica*, 27:1301–1306, 1987.
- [4] Y. Sakuma, O. Matsumura, and H. Takechi. Mechanical-properties and retained austenite in intercritically heat-treated bainite-transformed steel and their variation with Si and Mn additions. *Metallurgical & Materials Transactions A*, 22:489–498, 1991.
- [5] Y. Sakuma, O. Matsumura, and O. Akisue. Influence of C content and annealing temperature on microstructure and mechanical-properties of 400 C transformed steel containing retained austenite. *ISIJ International*, 31:1348–1353, 1991.
- [6] Y. Sakuma, O. Matsumura, and H. Takechi. Mechanical-properties and retained austenite in intercritically heat-treated bainite-transformed steel and their variation with Si and Mn additions. *Metallurgical & Materials Transactions A*, 22:489–498, 1991.
- [7] K. I. Sugimoto, A. Nagasaka, M. Kobayashi, and S. I. Hashimoto. Effects of retained austenite parameters on warm stretch-flangeability in TRIP-aided dual phase sheet steels. *ISIJ International*, 39:56–63, 1999.
- [8] H. K. D. H. Bhadeshia. TRIP-assisted steels? *ISIJ International*, 42:1059–1060, 2002.
- [9] P. J. Jacques. Transformation-induced plasticity for high strength formable steels. *Current Opinion in Solid State and Materials Science*, 8:259–265, 2004.
- [10] B.C. DeCooman. Structure-properties relationship in TRIP steels containing carbide-free bainite. *Current Opinion in Solid State and Materials Science*, 8:285–303, 2004.
- [11] W. W. Gerberich, G. Thomas, E. R. Parker, and V. F. Zackay. Metastable austenites: decomposition and strength. In *Second International Conference on Strength of Metals and Alloys*, pages 894–899, Ohio, USA, 1970. ASM International.
- [12] M. Santella, S. S. Babu, B. W. Riemer, and Z. Fang. Influence of microstructure on the properties of resistance spot welds. In S. A. David, T. DebRoy, J. A. Johnson, H. B. Smartt, and J. M. Vitek, editors, *Trends in Welding Research*, pages 605–609, Materials Park, Ohio, USA, 1999. ASM International.
- [13] H. L. Yi, S. K. Ghosh, W. J. Liu, K. Y. Lee, and H. K. D. H. Bhadeshia. Nonequilibrium solidification and ferrite in δ -TRIP steel. *Materials Science and Technology*, 25:in press, 2009.

- [14] NPL. MTDATA. Software, National Physical Laboratory, Teddington, U.K., 2006.
- [15] H.-S. Yang and H. K. D. H. Bhadeshia. Uncertainties in the dilatometric determination of the martensite–start temperature. *Materials Science and Technology*, 23:556–560, 2007.
- [16] G. G. Bentle and W. P. Fishel. Gamma loop studies in the Fe–Si and Fe–Si–Ti systems. *Trans. Am. Inst. Min. Metall. Engng.*, 206:1345–1348, 1956.

Table 1: The compositions achieved during manufacture, wt%. The alloys were manufactured as 34 kg ingots of $100 \times 170 \times 230$ mm dimensions using a vacuum furnace.

	Alloy 2	Alloy 3	Alloy 4	Alloy 5	Alloy 6	Alloy 7
C	0.37	0.40	0.40	0.41	0.37	0.39
Si	0.23	0.26	0.74	0.26	0.76	0.77
Mn	1.99	2.02	1.99	1.53	1.53	1.50
Al	2.49	2.50	2.39	2.30	2.91	3.35
Cu	0.49	—	0.49	0.49	—	—
P	0.02	0.02	0.02	0.02	—	—
S	0.0036	0.0013	0.0015	0.0014	0.0042	0.0045
N	0.0048	0.0032	0.0024	0.0030	0.0020	0.0022

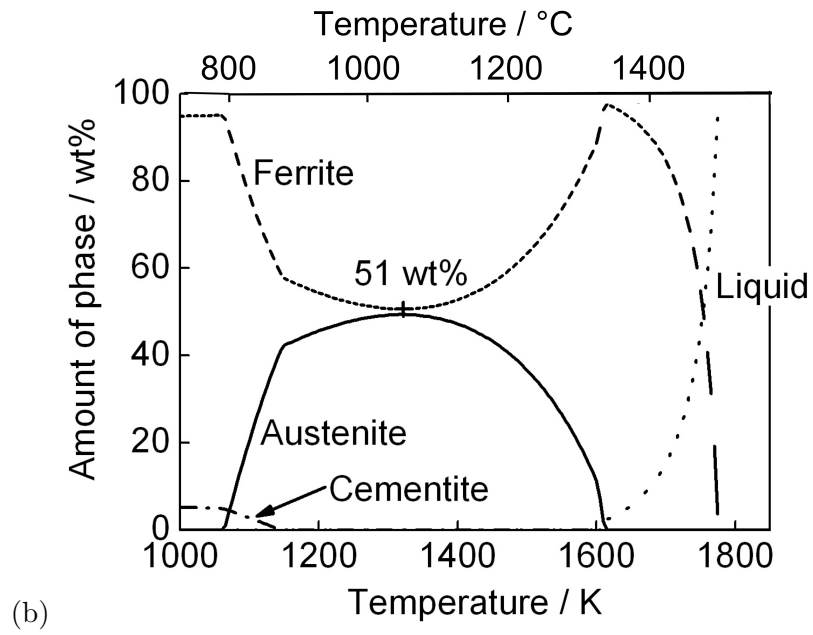
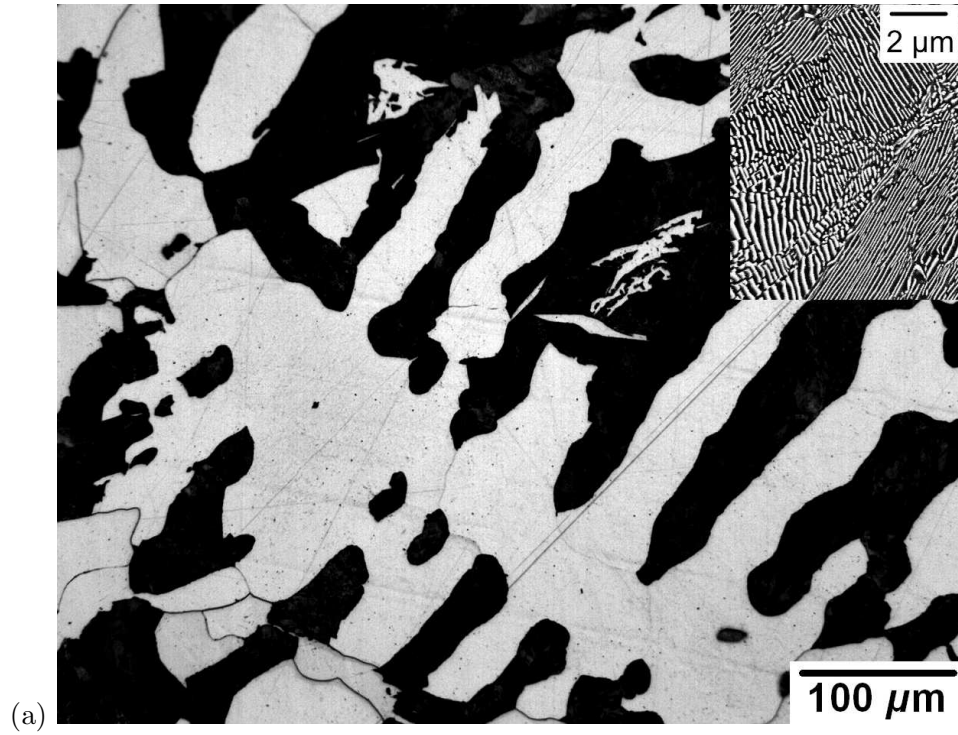


Figure 1: Alloy 2. (a) As-cast microstructure showing δ -ferrite dendrites; the dark regions are pearlitic, as illustrated at high magnification in the inset. (b) Calculated equilibrium phase diagram.

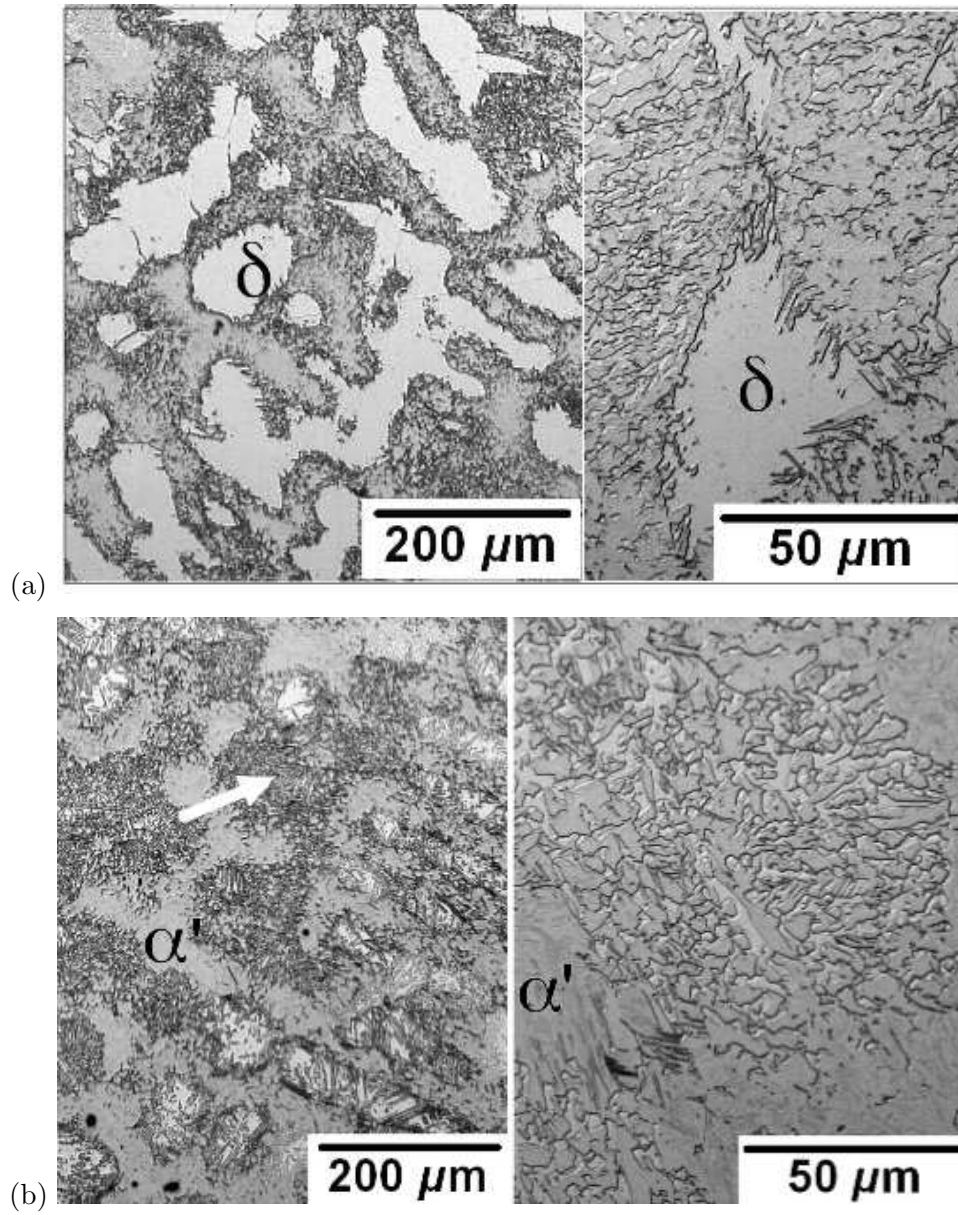


Figure 2: Alloy 2. (a) Heated to 800°C and quenched. The light-etching regions represent δ -dendrites and the darker regions are mixtures of martensite (austenite at 800°C) and ferrite. (b) Heated to 900°C and quenched. The arrow shows that the region which used to be the δ -ferrite, and which is now a mixture of martensite and residual ferrite.

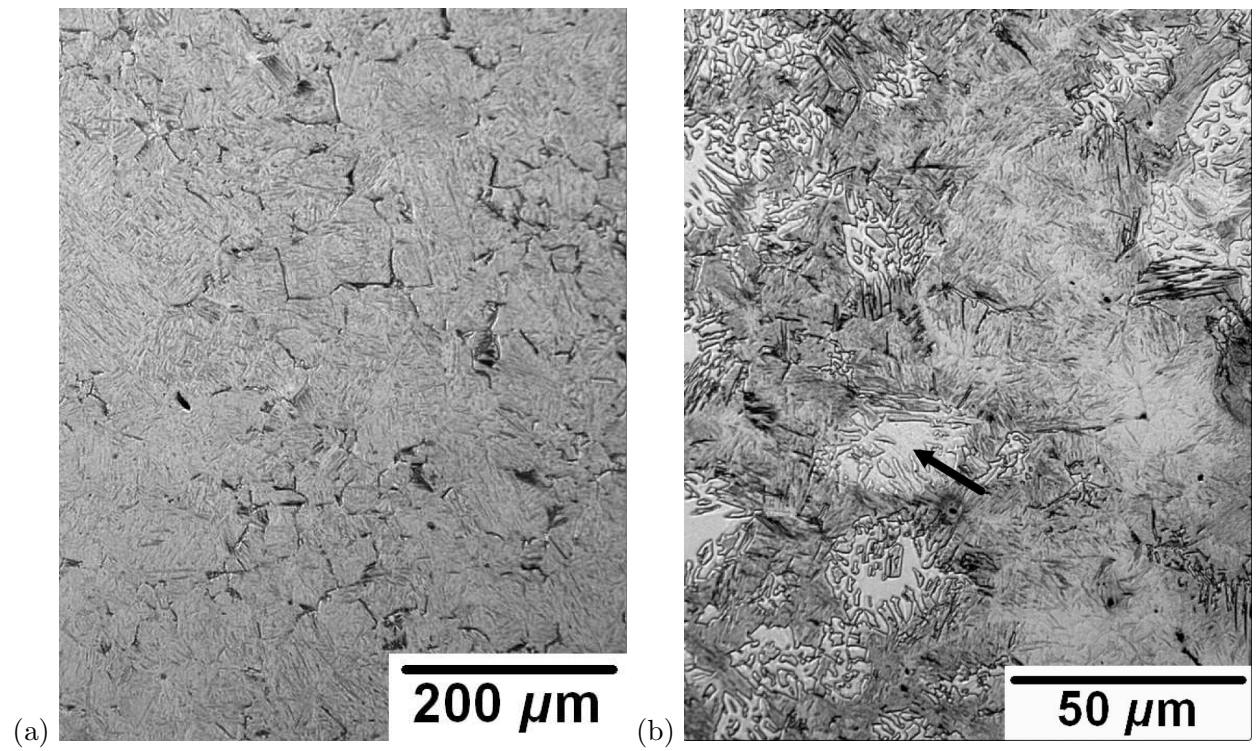


Figure 3: Alloy 2. (a) Heated to 1100°C and quenched. (b) Heated to 1400°C and quenched. The arrow indicates a ferrite forming in segregated regions of the sample, in shapes reminiscent of the solidification structure.

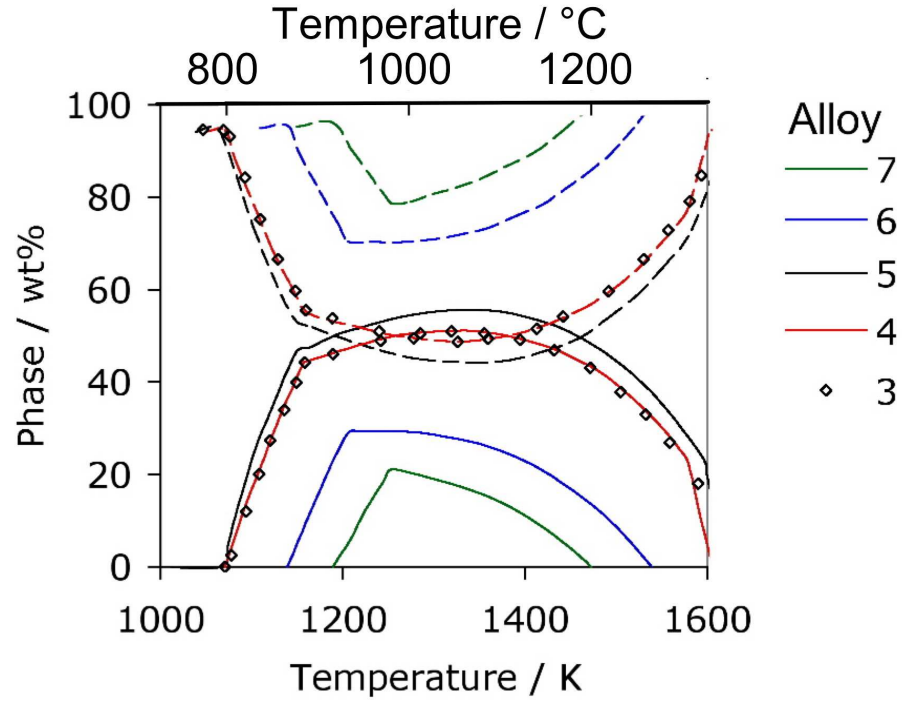


Figure 4: Calculated quantities of austenite (continuous lines) and ferrite (dashed lines). Alloy 3 is plotted as points in order to avoid confusion with Alloy 4. Although only austenite and ferrite are illustrated for clarity, the liquid and cementite phases were allowed to exist.

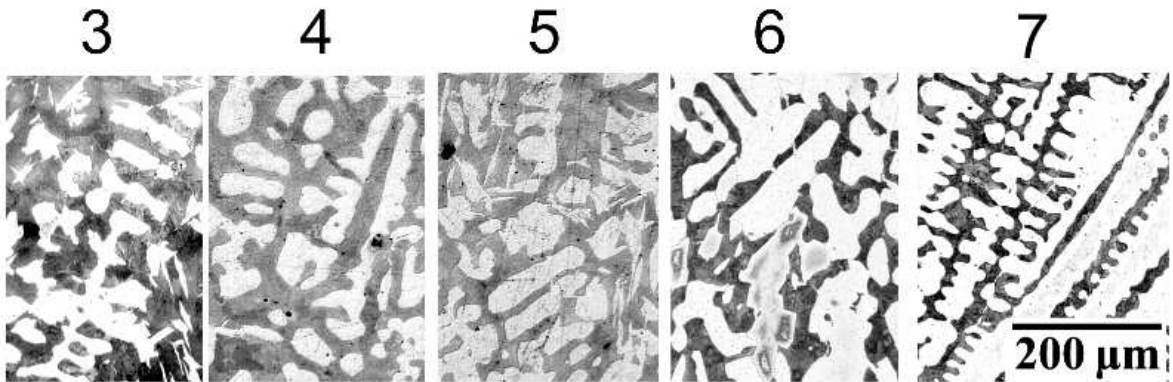


Figure 5: As-cast microstructures of Alloys 3–7.

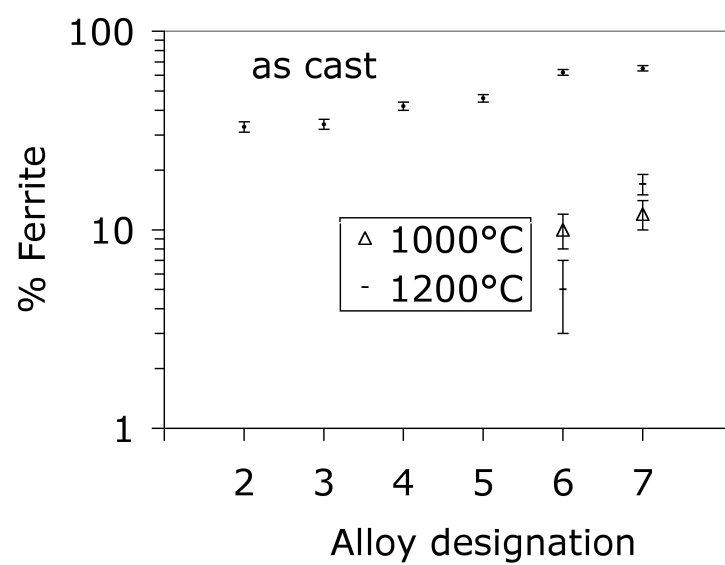


Figure 6: Volume percent of optically resolvable ferrite for cast, and reheated samples.

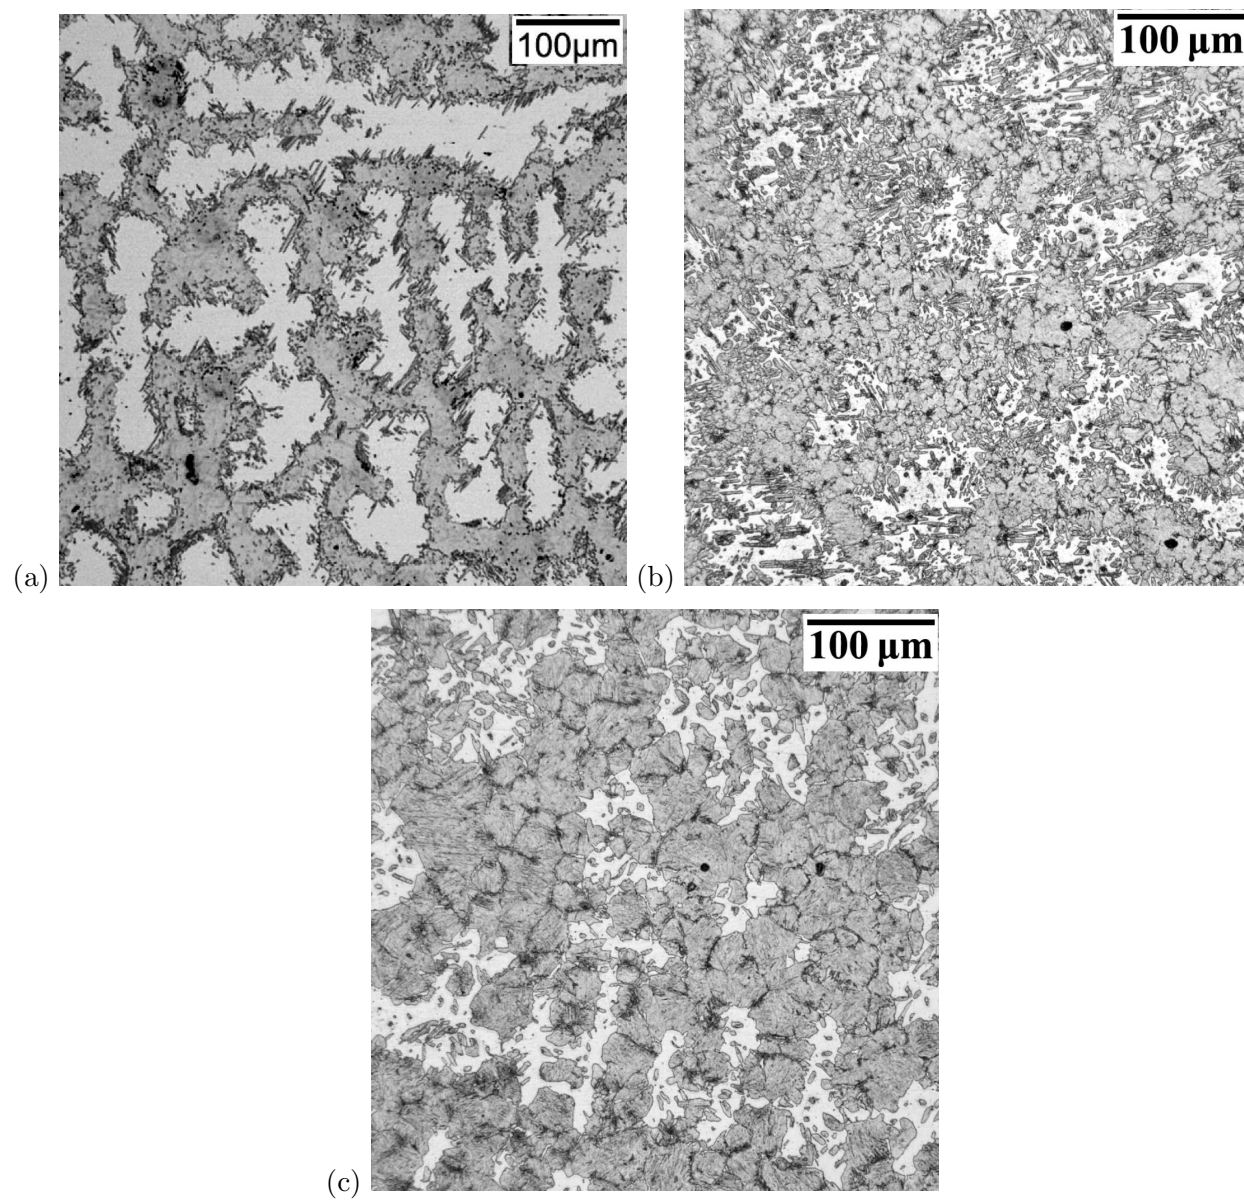


Figure 7: Alloy 7 following reheating to (a) 900°C, (b) 1000°C, (c) 1200°C.

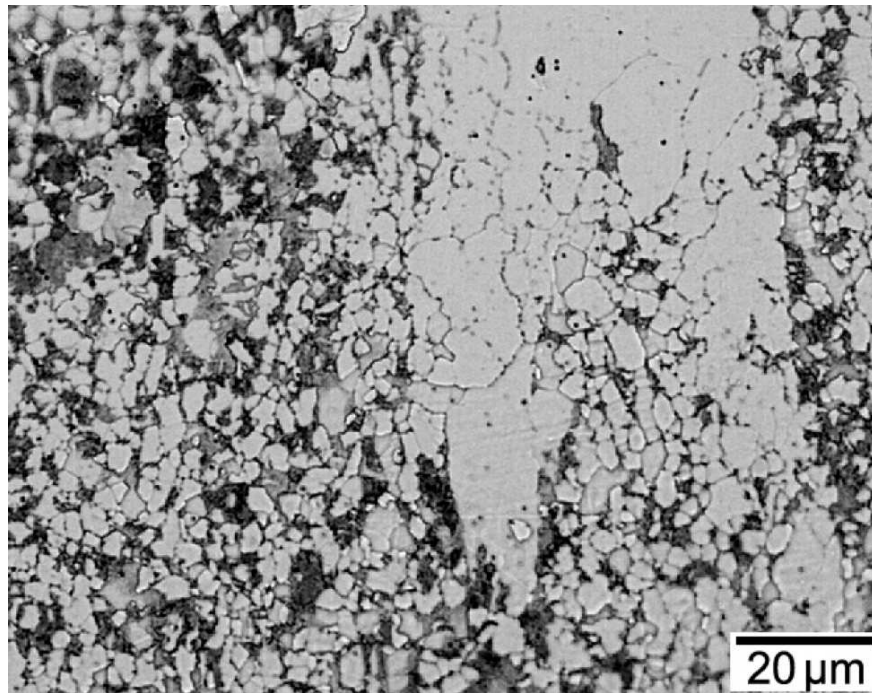


Figure 8: Alloy 7 after hot-rolling.